

# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

### INTRODUCTION

This guide provides contractors and applicators with the information required to successfully apply PPG PITT-THERM® 909 spray-on insulation (SOI) coating. The guide covers various questions and scenarios that may arise during application, with further information available within the technical data sheet or from your PPG representative. Please read this document carefully prior to commencing application.

---

### SURFACE PREPARATION

This product is suitable for applying directly to metal or over recommended primers. If applying over primer, all surface preparation and product application should be conducted in accordance with the product technical datasheet for that product. **However, it is recommended to only apply a total of 100-150 microns (4-6 mils) of primer, even if typically applied at higher film builds in other corrosion-under-insulation (CUI) situations.**

For application directly to steel, the following substrate conditions and temperatures are recommended:

- Steel surfaces should be abrasive blasted to Sa2.5 or minimum SSPC SP-6, blasting profile 50-150 microns (2-6 mils).
- Substrate temperature during application and curing should be above 5°C (41°F).
- Substrate temperature during application and curing should be 3°C (5°F) above dew point.
- Surface must be free of visible moisture.
- Product can be applied to hot surfaces at temperatures up to 149°C (300°F). See section on hot application below for further details.

---

### RECOMMENDED PRIMERS

Although various primers are suitable for use with this product, the recommended primer is PPG HI-TEMP 900. PPG HI-TEMP 900 can be used in all applications where PPG PITT-THERM® 909 is suitable (at temperatures of up to 260°C/500°F). Other options include SIGMATHERM® 230 for temperatures up to 230°C (446°F), and AMERLOCK 2 GF/SIGMASHIELD 2 and AMERLOCK 400 GF/SIGMASHIELD 400 for temperatures up to 200°C (392°F).

---

### STORAGE

Once product is received, store in a cool dry area. Temperatures below 32°C (90°F) are optimal for long-term stability. It is not recommended to open the part A container until ready to use as this can introduce moisture and cause the curing process to begin. If nitrogen (or other inert gas such as argon) is available, this can be used to fill the headspace of an opened part A container before resealing for later use.

# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

### COATING THICKNESS AND SPREAD RATE

#### Coating thickness

The coating thickness required will depend on the application conditions and purpose for use. Where personal protection is the main goal and no primer or topcoat is applied, 2.54 mm (100 mils) will provide safe-to-touch measured with a thermesthesiometer (ASTM C1055) up to 260°C (500°F) in most circumstances. If primed and/or topcoated, 4.32 mm (170 mils) will provide safe-to-touch up to 260°C (500°F) in most circumstances. In extreme environmental conditions, specifically air temperatures significantly above 23°C (75°F), it is recommended to add an additional 1.27 - 2.54 mm (50 - 100 mils).

As varying operating and environmental factors can affect thermal efficiency, please consult your PPG representative for exact film thicknesses required for both safe-to-touch and energy retention. The table below shows approximate coating surface temperature with various dry film thicknesses (DFT) and operating temperatures. These values assume standard laboratory conditions and will vary based on actual conditions in the field.

Operating Temp (°C)	38 (100°F)	93 (200°F)	149 (300°F)	204 (400°F)	260 (500°F)
<b>system</b>					
<b>DFT (mm)</b>	Coated Surface Temperatures (°C)				
2.54 (100 mils)	28 (82°F)	58 (136°F)	88 (191°F)	118 (245°F)	148 (299°F)
6.35 (250 mils)	26 (79°F)	51 (124°F)	76 (169°F)	101 (213°F)	126 (258°F)
12.7 (500 mils)	23 (74°F)	39 (103°F)	56 (132°F)	72 (161°F)	88 (190°F)

**Table 1: Coating surface temperature (not primed or topcoated) at different film thickness and operating temperatures**

#### Spread rate

Once the required film thickness is known, spread rate can be calculated by the formula below:

$$\text{Spread Rate (m}^2\text{/liter)} = (\% \text{ Volume Solids} \times 10) / \text{DFT (in microns)}$$

**Multiply by 40.75 to get ft<sup>2</sup>/US gal**

**PPG PITT-THERM® 909 spread rate = 0.10 m<sup>2</sup>/l for 6.35 mm DFT (4.04 ft<sup>2</sup>/US gal for 250 mils)**

**PPG PITT-THERM® 909 Volume Solids = 63%**

### PERSONAL PROTECTIVE EQUIPMENT

This product is for use only by professional applicators in accordance with information in this application guide, the product or technical data sheet, and the applicable material safety data sheet (MSDS). Applicators should use proper PPE including chemical-resistant clothing, gloves, safety goggles, and respirator. Refer to the appropriate MSDS before using this material. All use and application of this product should be performed in compliance with all relative federal, state, and local, health, safety, and environmental regulations or in compliance with all pertinent local, regional, and national regulations as well as good safety practices for painting, and in conformance with recommendations in SSPC PA 1, "Shop, Field and Maintenance Painting of Steel."



# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

### MIXING AND POT LIFE

No induction time is required.

Mix ratio by volume: base to hardener 16:1 (plus water addition below).

Mix parts A\* and B separately using a Jiffy mixer or paddle type blade. Mix until fully homogenized.

When properly mixed, the consistency of PPG PITT-THERM® 909 should be heavy-bodied (high viscosity) but free flowing, and there should be no lumps.

Once part B is fully mixed, add the following quantity of distilled water to Part B and mix thoroughly before adding to part A. The pre-marked cup that comes with the kit can be used for this purpose:

- 0.81 oz (24 ml) per 4-gal kit (15.1L kit)
- 9 oz (266 ml) per 44-gal kit (166.6L kit)

**The addition of water is required to guarantee proper cure times and humidity robustness.**

PPG PITT-THERM® 909 should be fully mixed without additional thinning. Any decision to thin the material should be made only after fully mixing and observing the condition of the mixed material. If thinner is required, only add up to 1% PPG Thinner 21-06 (AMERCOAT 65).

Once the material is mixed, the pot life is expected to be 8 hours at 20°C (68°F) with the container covered during application.

\*Part A may contain a solid layer at the top of the can when first opened. This is normal and should be thoroughly mixed as directed above.

---

### APPLICATION EQUIPMENT

PPG PITT-THERM® 909 is suitable for multiple application methods provided that pressure during fluid transfer does not exceed 3.44 MPa (500 PSI). Below is a list of equipment options that can be utilized to apply the coating.

#### **Pneumatic Piston Pump (Graco President 10:1) – recommended for large application areas**

Use with Graco STX Air Spray Trigger Gun, Model 17Y910 Series J23A:

- 4 mm Fluid Nozzle with W4H WideTex Disc
  - Fluid Pressure: 0.172-0.241 MPa (1.72-2.41 bar; 25-35 PSI)
  - Pump Pressure: 1-1.38 MPa (1-13.7 bar; 145-200 PSI)
  - Air Pressure: 0.38-0.45 MPa (3.8 - 4.5 bar; 55-65 PSI)
  - Material hose diameter: 19-25 mm (3/4-1 in)
  - Air hose diameter: 9.5-19 mm (3/8-3/4 in)
- 
- Mount onto drum lid by placing the pump's fluid intake rod through the drum cover's open bung or clamp to inside wall of drum. If removing lid from open-head drum to mount the pump, keep the coating material covered as best as possible to avoid premature curing of the material in the drum.
  - Other low ratio piston pumps will work depending on the size and length of hose needed for the job.
  - Pre-condition the pump and lines with PPG thinner 21-06 (Amercoat 65) prior to application to confirm pump and hose lines are completely clean.


# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

### HVLP with pressure pot – recommended for small application areas or repairs

- Nozzle orifice: approx. 3mm (0.11 in).
- Nozzle pressure: approx. 0.207-0.241 MPa (2.06-2.40 bar; 30-35 PSI)
- Pot pressure: 0.241-0.275 MPa (2.40-2.75 bar; 35-40 PSI)

**Image 1-4: Graco President 10:1 pump (left) with gun Model 204000 (middle-left), gun Model 17Y910 (middle-right), and telescoping spray pole (right)**

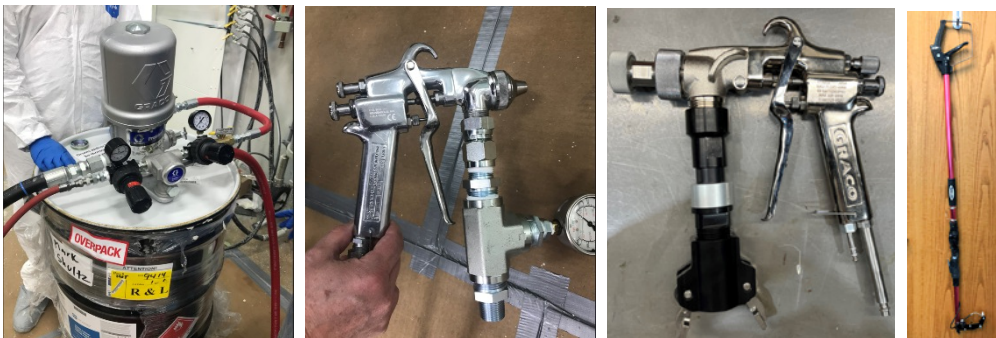

#### Other Options:

- Air-powered diaphragm pumps with a texture sprayer can also be used. It is possible to apply PPG PITT-THERM® 909 using Graco's GTX 2000 EX machine if the equipment is modified to ensure solvent resistance. Contact a PPG representative for further information on modification required and recommended application parameters.
- To improve ergonomics of spraying on horizontal or hard to reach vertical surfaces, a telescoping spray pole such as the one pictured herein can be used with the recommended application guns above.

### APPLICATION TIPS & TECHNIQUES

PPG PITT-THERM 909 can be applied from 2.54 - 6.35 mm (100-250 mils) DFT per coat up to 12.7 mm (500 mils) total.

The application parameters given in the previous section are recommended starting points. Depending on environmental conditions, it may be required to further adjust the air or material pressures or nozzle orifice size to achieve optimal appearance and reduce overspray.

Image 5 shows the appearance of the coating with too much air pressure and overspray. Image 6 shows the optimal finish. Provided that no loose material is on the surface, the coating in both images will still perform as intended. However, for the best appearance and uniformity in thermal properties, it is best to adjust equipment as necessary.



**Image 5 and 6: Rougher texture on the left (still functional) versus optimal texture on the right**

# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

If a smoother texture is desired (for appearance only) after application of the coating, there are two options available:

1. As soon as the coating is tack-free, a roller soaked in the recommended thinner can be lightly rolled over the surface of the coating to smooth out any roughness.
2. Before applying the next layer or topcoat, the surface of the coating can be lightly sanded using a fine grit sandpaper.

**Any overspray or dust created from sanding should be brushed or blown off completely before applying subsequent coats.**

In addition to equipment parameters, other important guidelines include:

- Keep a distance of at least 30–46 cm (12–18 in) from the surface being sprayed to avoid excessive dry spray.
- The coating fan should remain perpendicular to the surface to minimize overspray.
- When building DFT, apply approximately 760 - 1270 microns (30 - 50 mil) per pass wet-on-wet, allowing a flash time of least 1-2 minutes after each 2540 microns (100 mil) wet film thickness (WFT). Do not allow the coating to reach dry-to-touch between passes. Once the coating is dry-to-touch, the minimum overcoat windows below will need to be followed to prevent delamination between coats.

### HOT APPLICATION

PPG PITT-THERM® 909 can be applied on hot substrates up to 149°C (300°F). When applying to surfaces above 66°C (150°F), use the following techniques:

- Build the first 1270-2540 microns (50-100 mil) WFT with quick 250 - 380 microns (10-15 mil) passes. Allow flash time of 1-2 minutes between passes to avoid blisters from solvent popping.
- The remaining WFT can be build up as normal.
- Please note that the maximum overcoat window of the primers will be significantly reduced when applied to a hot substrate. Follow the recoat windows for elevated temperatures in the technical datasheet for your chosen primer.

### CURE AND RECOAT SCHEDULE

Table 2 below shows cure times for PPG PITT-THERM® 909 at various temperatures and at 50% relative humidity (RH). RH has minimal effect on cure speed and this product is suitable for application at humidity ranging from 10-95%, given that the surface is free from visible moisture.

Curing time for DFT up to 6.35 mm (250 mils) at 50% RH		
Substrate temperature	Dry to touch	Dry to handle
5°C (41°F)	2 hours	2 days
25°C (77°F)	1.25 hours	26 hours
40°C (104°F)	1 hour	23 hours
93°C (200°F)	10 min	15 hours
149°C (300°F)	10 min	14 hours

**Table 2: Cure Times**



## PPG PITT-THERM® 909

## Spray-on insulation coating application guide

Overcoating Intervals up to 250 mils (6.35 mm) DFT and 50% RH				
Overcoating with...	Interval	5°C (41°F)	25°C (77°F)	40°C (104°F) and above
Itself	Min	24 hours	16 hours	7 hours
	Max	30 days	30 days	30 days
Topcoat	Min	24 hours	20 hours	16 hours
	Max	14 days	14 days	14 days

**Table 3: Overcoating Intervals**

After application, PPG PITT-THERM® 909 can be recoated after a minimum of 16 hours and a maximum of one month at 25°C (77°F). At lower temperatures, allow to cure for 20-24 hours before recoating. For elevated temperatures, please consult with a PPG representative.

**REPAIR**

PPG PITT-THERM® 909 hardens as it cures and is hard and strong enough to walk on the next day. If the coating sustains damage which is caused by a sharp or heavy object (either during application or at a later date), the following two methods are suitable for repair:

1. HVLP with pressure pot as outlined in the section “Application Equipment” can be used to repair damaged areas.
2. Small areas of damage <15 cm (<6 in) wide can be repaired using a trowel. Apply the coating evenly using a clean trowel and follow the same DFT recommendations as with spray application.

**Image 7: Trowel repair****CLEANUP**

Equipment can be cleaned using PPG Thinner 21-06 (AMERCOAT 65) or any other approved organic solvent. Any unused mixed coating will cure in the can and can be disposed of according to local regulations.

For information on storing excess coating, please see the section on storage above.

**RECOMMENDED TOPCOATS**

Topcoat is not required for PPG PITT-THERM® 909 but may be applied to achieve a desired color. Suitable topcoats include PPG HI-TEMP 1000 and PPG PITT-TECH PLUS EP DTM. Where the surface temperature of PPG PITT-THERM® 909 is likely to exceed 121°C (250°F), PPG HI-TEMP 1000 is recommended.



# PPG PITT-THERM® 909

## Spray-on insulation coating application guide

### LIMITATION OF LIABILITY

IN NO EVENT WILL PPG BE LIABLE UNDER ANY THEORY OF RECOVERY (WHETHER BASED ON NEGLIGENCE OF ANY KIND, STRICT LIABILITY OR TORT) FOR ANY INDIRECT, SPECIAL, INCIDENTAL, OR CONSEQUENTIAL DAMAGES IN ANY WAY RELATED TO, ARISING FROM, OR RESULTING FROM ANY USE MADE OF THE PRODUCT. The information in this sheet is intended for guidance only and is based upon laboratory tests that PPG believes to be reliable. PPG may modify the information contained herein at any time as a result of practical experience and continuous product development. All recommendations or suggestions relating to the use of the PPG product, whether in technical documentation, or in response to a specific inquiry, or otherwise, are based on data, which to the best of PPG's knowledge, is reliable. The product and related information is designed for users having the requisite knowledge and industrial skills in the industry and it is the end-user's responsibility to determine the suitability of the product for its own particular use and it shall be deemed that Buyer has done so, as its sole discretion and risk. PPG has no control over either the quality or condition of the substrate, or the many factors affecting the use and application of the product. Therefore, PPG does not accept any liability arising from any loss, injury or damage resulting from such use or the contents of this information (unless there are written agreements stating otherwise). Variations in the application environment, changes in procedures of use, or extrapolation of data may cause unsatisfactory results. This sheet supersedes all previous versions and it is the Buyer's responsibility to ensure that this information is current prior to using the product. Current sheets for all PPG Protective & Marine Coatings Products are maintained at [www.ppgpmc.com](http://www.ppgpmc.com). The English text of this sheet shall prevail over any translation thereof.

---

The PPG logo is a registered trademark and Bringing innovation to the surface and all other trademarks herein are property of the PPG group of companies.

